LONG CONTINUOUSLY CHIRPED FIBER BRAGG GRATINGS FOR COMPENSATION OF LINEAR - AND 3rd ORDER - DISPERSION

Morten Ibsen, Michael K. Durkin, Karin Ennser, Martin J. Cole and Richard I. Laming.

Optoelectronics Research Centre, University of Southampton, Southampton, S017 IBJ,UK.

Abstract—For the first time long broadband chirped fiber Bragg gratings with a dispersion profile designed to compensate 3rd order-dispersion are presented. These results demonstrate how the increased demands for dispersion compensation at very high bit-rates can be met using chirped fiber Bragg gratings.

INTRODUCTION

The field of fiber Bragg gratings is now well established with devices finding many important applications. In particular chirped fiber Bragg gratings have already proven their suitability as chromatic dispersion compensators in a series of experiments [1,2] where they have been incorporated in real systems at 10 Gbit/s with excellent results. Furthermore they have been shown to allow 40 Gbit/s error-free transmission at 1.55 pm over 109 km of non-dispersion shifted fiber as we recently reported [3]. As the bit rates are being increased the effect of higher order dispersion and polarization mode dispersion starts to become a limiting factor on the recovery of the data after transmission over long distances. Higher order dispersion therefore needs to be compensated in order to explore the fill potential of the already installed and future fiber links. Chirped fiber gratings are therefore attractive alternatives to other proposed dispersion compensation schemes because they can be designed to compensate for both 2nd- and 3rd-order dispersion simultaneously over large bandwidths.

In this paper we report long continuously chirped broadband fiber Bragg gratings designed to compensate both the 2nd and 3rd order dispersion of the new reduced dispersion fiber types such as AT&T "TrueWave". These fiber types are important since the chromatic dispersion is small enough to allow a large number of channels to be transmitted over longer distances than standard fiber without dispersion compensation whilst being large enough to suppress four wave mixing. However, unfortunately the transmission capacity of this fiber will be limited by the uncompensated 2nd and increased 3rd order dispersion. Typical values for which are ~3.2 ps/nm/km and 0.19 ps/nm²/km at 1556 run [4].

We report long continuously chirped broadband fiber Bragg gratings designed to compensate for 317 km and 627 km of transmission in dispersion reduced fibers. As an example we chose dispersion characteristics matching AT&T "TrueWave" fiber.

EXPERIMENT

1 m long continuously chirped gratings are written using a modified version of the moving fiber/phase-rnask scanning-beam technique [5] and an intra-cavity frequency doubled Argon laser producing 80 mW of UV-light at 244 nm, Deuterium loaded fiber with a numerical aperture on ~0.2 is used as host fiber. The gratings are written in pairs with and without 3rd order dispersion in order to demonstrate the differences in the dispersion slopes. The time taken to write each grating is 17 min. The gratings arc characterized with a resolution of 10 pm using a tunable laser together with a high precision wave meter.

Varying the wavelength linearly along the length of the grating during writing gives a linear time delay over the full length of the grating. By varying the wavelength with a quadratic term on top of the linear dispersion along the length of the grating a quadratic change in the dispersion with wavelength and hence a quadratic change in the delay of the grating is achieved.

Fig. 1 shows the reflection, time delay and deviation from linear time delay spectra for two 1 m long 9.5 run chirped gratings, with Fig. 1a showing the grating with linear dispersion of 1016 ps/nm ± 40 ps

Southampton Photonics (US) 170 Knowles Drive
Suite 2 Los Gatos, California, USA 95032
tel: (408) 866-0472 fax: (408) 865-1816
www.southamptonphotonics.com

Southampton Photonics (UK) Phi House Enterprise Road
Chilworth Science Park Southampton , United Kingdom SO16 7NS
tel: +44 (0) 23 8076 6070 fax: +44 (0) 23 8076 0311
email: info@southamptonphotonics.com

and Fig. 1b the corresponding 1 m grating with average dispersion of 1016 ps/nm and a deviation from the linear dispersion slope on ~680 ps at the bandwidth etches of the grating. Both gratings compensate for 317 km of chromatic dispersion in the fiber discussed above, with the second grating compensating for the additional 3rd order dispersion component theoretically determined from (0.5 x 0.19 ps/nm²h x 317 km x (0.5 x 9.5 nm)²). Fig 2 shows two 1 m gratings with bandwidths on 4,8 nm and linear dispersions of 2025 ps/mn, equivalent to 627 km of same fiber. Fig. 2b shows in addition a quadratically chirped grating designed to compensate the 3rd order dispersion that causes a deviation from linear dispersion on ~350 ps at the bandwidth etches with a theoretically value calculated from (0.5 x 0.19 ps/nm²/kmx 627 km x (0.5 x 4.8 nm)²) to be 343 ps.

DISCUSSION

The deviations in the reflection spectra and time delay curves presented are due to stiching type errors in the phase-mask used. This is seen because the same type of underlying structure is present at both series of plots. Normalization of the deviation from the linear time delay on Fig. 1b vs. the deviation from the linear time delay in Fig. 1a would then show the pure 3rd order term. This is shown on Fig. 1b as a dotted curve on the deviation from the linear time delay. Furthermore are environmental changes during writing are a limiting factor in the reduction of the time-delay ripples/deviations.

Design of fiber gratings for 3rd order dispersion compensation of standard single-mode fibers with a chromatic dispersion of 17 ps/nm/km and a dispersion slope of 0.08 ps/nm²/km is more critical. For a 1 m long chirped grating designed to compensate transmission through 100 km of standard fiber the 3rd order component would give rise to a deviation from the linear time delay on the etches of a 5.7 nm bandwidth chirped grating of ~33 ps. As the deviation from the linear time delay is ~±30-40 ps for the linearly chirped gratings this task is not realistic at the present time. Improvements on the grating writing set-up are been undertaken and at the time of the conference we hope to present results for 3rd order dispersion compensation of standard fiber.

CONCLUSION

We have demonstrated 1 m long chirped fiber gratings with dispersion profiles designed to cope with both linear- and 3rd order dispersion. In this paper these gratings have been designed to compensate 317 km and 627 km of the dispersion reduced AT&T "TrueWave" fiber. We strongly believe that this shows that the technology of chirped fiber Bragg gratings has matured and is ready to take a leading role in the area of dispersion compensating devices.

ACKNOWLEDGEMENTS

This work was partly supported by Pirelli Cavi SpA.

REFERENCES

1. W.H. Loh, R.I. Laming, A.D. Ellis, and D. Atkinson: "Dispersion compensated 10 Gbit/s transmission over 700 km of standard single mode fiber with 10 cm chirped fiber grating and duobinary transmitter", Proceeding OFC '96, paper PD30, San Jose, USA, 1996.
2. M.J. Cole, H. Geiger, R.I. Laming, S.Y. Set, M.N. Zervas, W.H. Loh and V. Gusmeroli: "Broadband dispersion-compensating chirped fiber Bragg gratings in 10 Gbit/s NRZ 110 km non-dispersion-shifted fibre link operating at 1.55 pm", *Electron. Left.,* 33, (l), pp. 70-71,1997.
3. L. Dong, M.J. Cole, A.D. Ellis, M. Durkin, M. Ibsen, V. Gusmeroli and R.I. Laming: "40 Gbit/s 1.55 µm Transmission over 109 km of non-dispersion shifted fiber with long continuously chirped fiber gratings", in proceedings of, OFC'97,PD6, San Jose, USA, 1997.
4. http://www.steinkuehler.de/truewave25.htm.
5. M. J. Cole, W, H, Loh, R. I. Laming, M. N. Zervas and S. Barcelos: "Moving fiber/phase-mask scanning beam technique for enhanced flexibility in producing fiber gratings with a uniform phase-mask", *Electron. Lett.,* 1995,31, (17), pp. 70-71.

Southampton Photonics (US) 170 Knowles Drive
Suite 2 Los Gatos, California, USA 95032
tel: (408) 866-0472 fax: (408) 865-1816
www.southamptonphotonics.com

Southampton Photonics (UK) Phi House Enterprise Road
Chilworth Science Park Southampton , United Kingdom SO16 7NS
tel: +44 (0) 23 8076 6070 fax: +44 (0) 23 8076 0311
email: info@southamptonphotonics.com

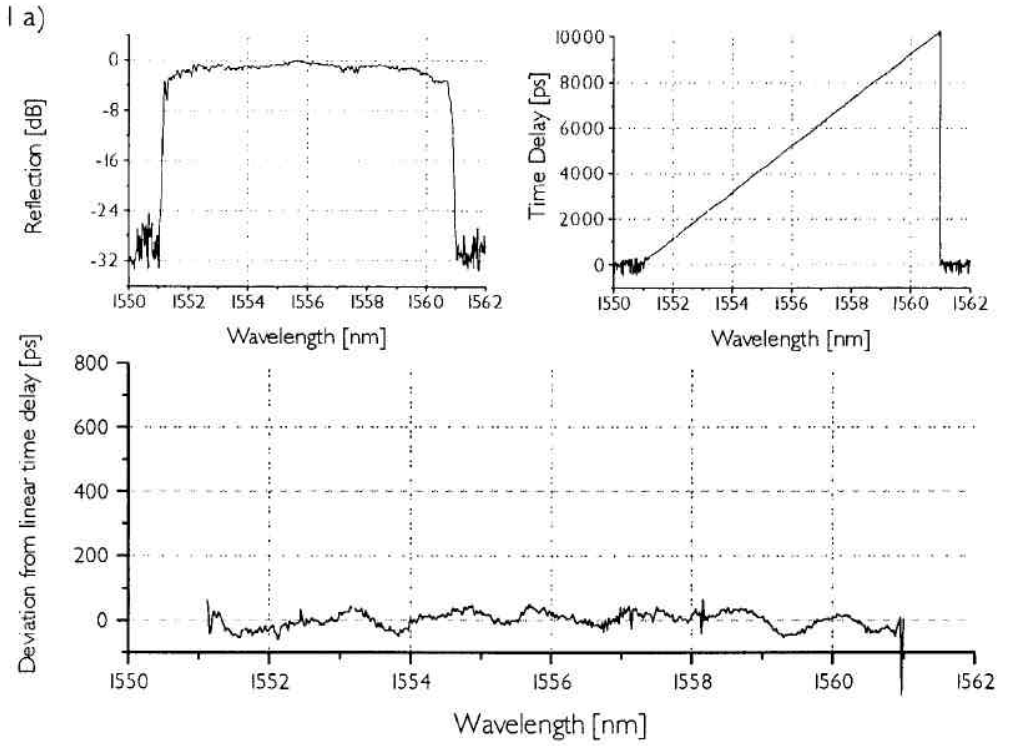


Figure 1a. - Rejection spectrum, time delay and deviation from linear time delay of a 1 m long linearly chirped grating with a bandwidth of 9.S nm and a dispersion slope of 1016 ps/nm

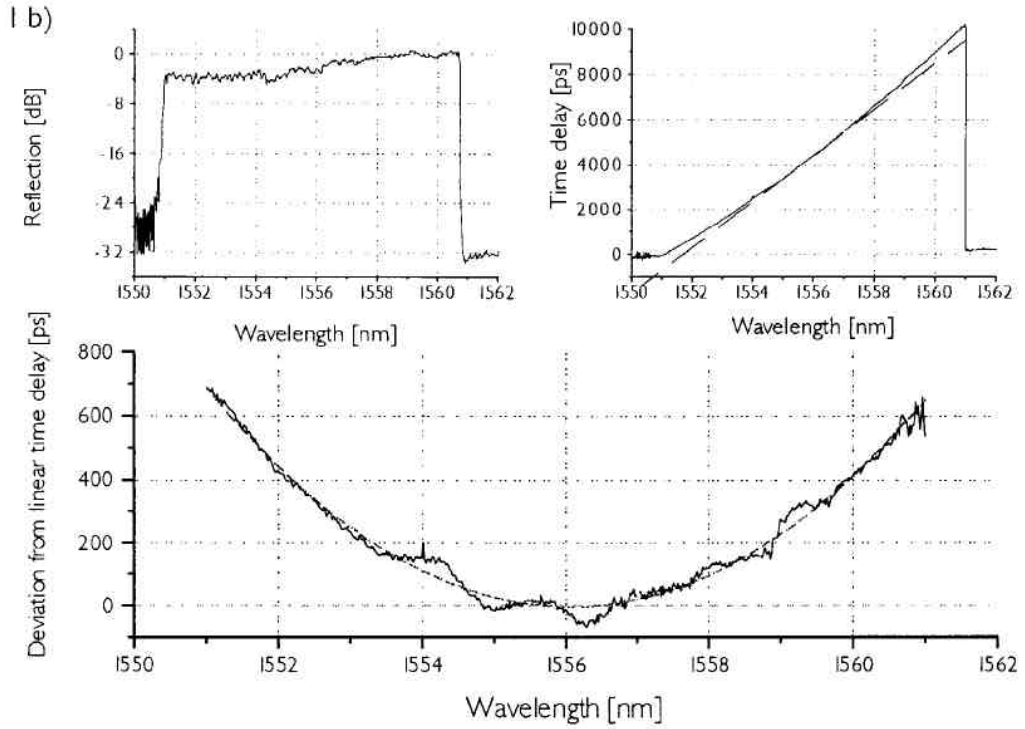


Figure 1b. - Reflection spectrum, time delay and deviation from linear time delay of a 1 m long quadratically chirped grating with a bandwidth of 9.S nm and a linear dispersion of 1O16 ps/nm and a maximum deviation of 680 ps at the etches of the bandwidth.

Southampton Photonics (US) 170 Knowles Drive
Suite 2 Los Gatos, California, USA 95032
tel: (408) 866-0472 fax: (408) 865-1816
www.southamptonphotonics.com

Southampton Photonics (UK) Phi House Enterprise Road
Chilworth Science Park Southampton , United Kingdom SO16 7NS
tel: +44 (0) 23 8076 6070 fax: +44 (0) 23 8076 0311
email: info@southamptonphotonics.com

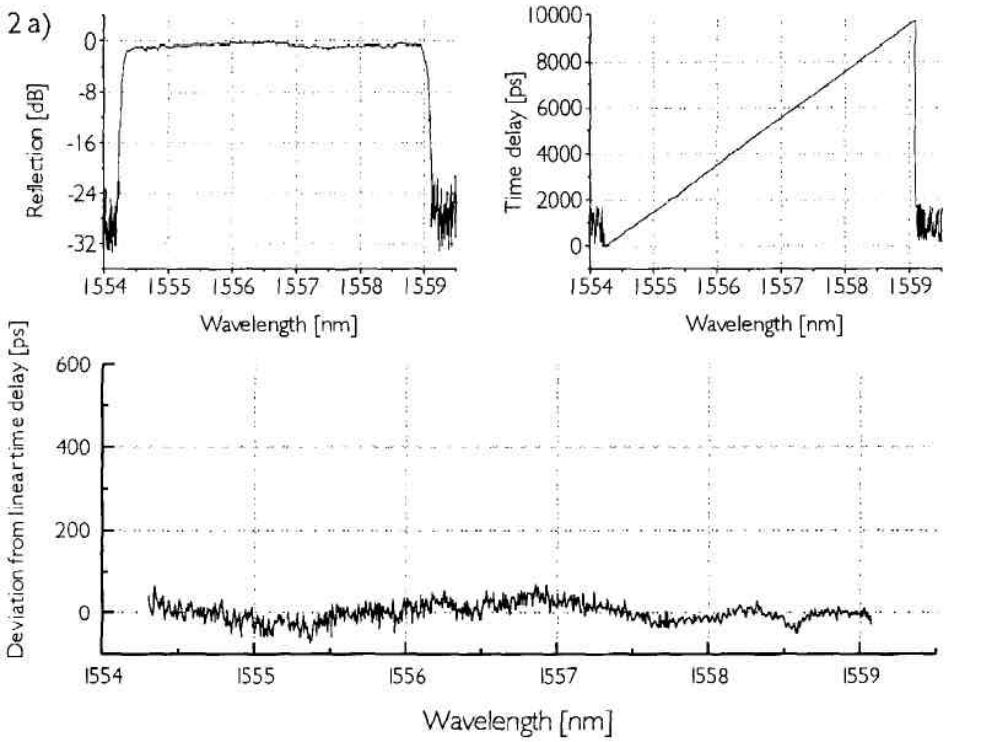


Figure 2a. - Reelection spectrum, time delay and deviation from linear time delay of a 1 m long linear chirped grating with a bandwidth of 4.8 nrn and a dispersion slope of 2025 ps/nm.

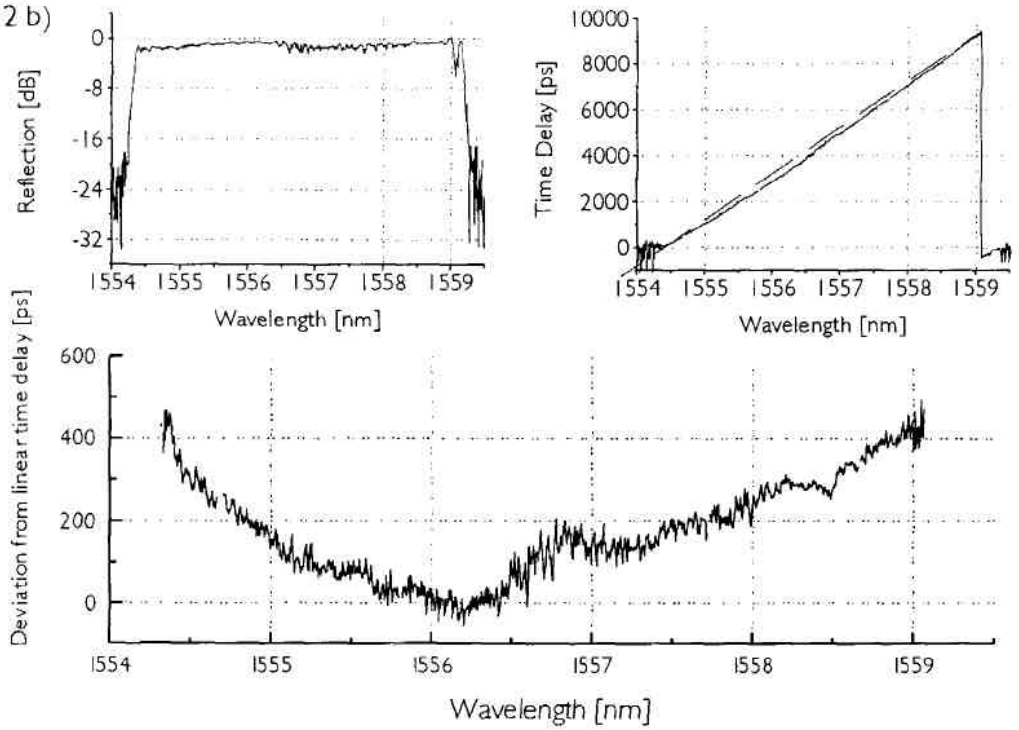


Figure 2b. - Rejection spectrum, time delay and deviation from linear time delay of a 1 m long quadratically chirped grating with a bandwidth of 4.8 nm and a linear dispersion slope of 2025 ps/nm and a maximum deviation of 343 ps at the etches of the bandwidth.

Southampton Photonics (US) 170 Knowles Drive
Suite 2 Los Gatos, California, USA 95032
tel: (408) 866-0472 fax: (408) 865-1816
www.southamptonphotonics.com

Southampton Photonics (UK) Phi House Enterprise Road
Chilworth Science Park Southampton , United Kingdom SO16 7NS
tel: +44 (0) 23 8076 6070 fax: +44 (0) 23 8076 0311
email: info@southamptonphotonics.com